

AD-A058 027

VIRGINIA UNIV CHARLOTTESVILLE DEPT OF MATERIALS SCIENCE F/G 20/2  
MICROSTRUCTURAL OBSERVATIONS ON HIGH STRENGTH POLYCRYSTALLINE I--ETC(U)  
AUG 78 H G WILSDORF, O T INAL, L E MURR N00014-75-C-0691  
UVA/525321/MS78/102 NL

UNCLASSIFIED

| OF |

AD  
A058027

PDF




END  
DATE  
FILMED  
10-78  
DDC

ADA058027

AD No. \_\_\_\_\_

DDC FILE COPY



LEVEL <sup>A</sup>

(12)

RESEARCH LABORATORIES FOR THE ENGINEERING SCIENCES

SCHOOL OF ENGINEERING AND  
✓ APPLIED SCIENCE

UNIVERSITY OF VIRGINIA

Charlottesville, Virginia 22901

A Technical Report

MICROSTRUCTURAL OBSERVATIONS ON HIGH STRENGTH  
POLYCRYSTALLINE IRON WHISKERS

Contract No. N00014-75-C-0691 *new*

Submitted to:

Office of Naval Research  
Department of the Navy  
800 N. Quincy Street  
Arlington, VA 22217

Submitted by:

H. G. F. Wilsdorf  
Department of Materials Science  
University of Virginia  
Charlottesville, Virginia

Osman T. Inal  
Lawrence E. Murr  
Department of Metallurgical and Materials Engineering  
New Mexico Institute of Mining and Technology  
Socorro, NM 87801


78 08 08 147 DDC

Report No. UVA/525321/MS78/102

August 1978

AUG 25 1978

A

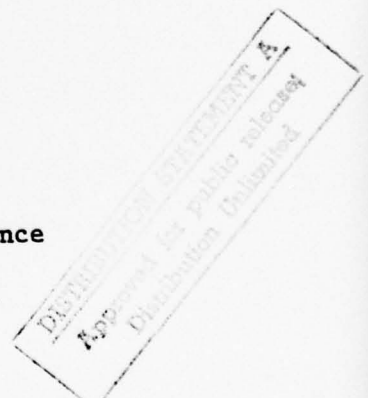

### RESEARCH LABORATORIES FOR THE ENGINEERING SCIENCES

Members of the faculty who teach at the undergraduate and graduate levels and a number of professional engineers and scientists whose primary activity is research generate and conduct the investigations that make up the school's research program. The School of Engineering and Applied Science of the University of Virginia believes that research goes hand in hand with teaching. Early in the development of its graduate training program, the School recognized that men and women engaged in research should be as free as possible of the administrative duties involved in sponsored research. In 1959, therefore, the Research Laboratories for the Engineering Sciences (RLES) was established and assigned the administrative responsibility for such research within the School.

The director of RLES—himself a faculty member and researcher—maintains familiarity with the support requirements of the research under way. He is aided by an Academic Advisory Committee made up of a faculty representative from each academic department of the School. This Committee serves to inform RLES of the needs and perspectives of the research program.

In addition to administrative support, RLES is charged with providing certain technical assistance. Because it is not practical for each department to become self-sufficient in all phases of the supporting technology essential to present-day research, RLES makes services available through the following support groups: Machine Shop, Instrumentation, Facilities Services, Publications (including photographic facilities), and Computer Terminal Maintenance.

9

A Technical Report,

6

MICROSTRUCTURAL OBSERVATIONS ON HIGH STRENGTH POLYCRYSTALLINE  
IRON WHISKERS.

Contract No. N00014-75-C-0691

15

Submitted to:

Office of Naval Research  
Department of the Navy  
800 N. Quincy Street  
Arlington, VA 22217

10

Submitted by:

H. G. F. Wilsdorf,  
Department of Materials Science  
University of Virginia  
Charlottesville, Virginia

Osman T. Inal  
Lawrence E. Murr

Department of Metallurgical and Materials Engineering  
New Mexico Institute of Mining and Technology  
Socorro, NM 87801

12 18 p.

Department of Materials Science  
RESEARCH LABORATORIES FOR THE ENGINEERING SCIENCES  
SCHOOL OF ENGINEERING AND APPLIED SCIENCE  
UNIVERSITY OF VIRGINIA  
CHARLOTTESVILLE, VIRGINIA

14

Report No. UVA/525321/MS78/102

11 August 1978

Copy No. \_\_\_\_\_

78 08 08 147

402 762

set



# ABSTRACT

Polycrystalline iron whiskers produced by chemical vapor decomposition in the presence of a magnetic field have been investigated in regard to their microstructure and composition by transmission electron microscopy, field ion microscopy, and by X-ray and electron diffraction techniques. It was found that the whiskers consisted of a unique and complex microdispersion of iron oxides, iron carbide, and atomic carbon which bond the very small alpha-iron crystallites into a non-porous microstructure of high integrity. The mixing of strong covalent bonding with metallic bonding is proposed to explain the exceptionally high tensile strength of the whiskers.

ACCESSION BY	
HTD	
QUC	
QUC	
JUL 1964	
Letter on file	
BY	
REMARKS	
A	

## INTRODUCTION

Lashmore et al.<sup>(1)</sup> have recently reported on the microstructure of polycrystalline iron whiskers made by the Schladitz process<sup>(2,3)</sup> where the thermal decomposition of iron pentacarbonyl in the presence of a magnetic field produces polycrystalline filaments consisting of fine grains of  $\alpha$ -Fe 50-200 Å in diameter. In the present investigation, an attempt was made to provide additional evidence for the microstructural integrity which is thought to be responsible for the high tensile strength measured to be as high as 800 MPa. In particular, since it was recognized that overlapping diffraction contrast effects made it difficult to accurately identify individual crystalline features in the transmission electron microscope, it was decided to prepare emission end forms of the whiskers to observe the surface atomic structure by field-ion microscopy. This paper summarizes the results of a combined study employing transmission electron microscopy and field-ion microscopy. X-ray and electron diffraction data have been consulted to obtain a more definite interpretation of micrographical results.

### 1. Experimental

Schlaiditz iron whiskers prepared as described previously<sup>(2,3)</sup> will be influenced structurally by the growth conditions which exist in the CVD reaction space. The whiskers were grown in an apparatus designed by H. Schladitz and built by his Physikalisch-Chemisches Forschungslabor, Munich, Germany. The machine was modified recently by the staff at the University of Virginia for this research by replacing the original carbonyl pump with a pressure operated carbonyl injector and by

changing the gas flow geometry in the reaction space.  $N_2$  was used as the main carrier gas directly taken from a commercially available cylinder; the flow rate was  $30 \text{ cm}^3/\text{sec}$ . Whisker growth was initiated at  $265^\circ\text{C}$  and lowered within 3 minutes to  $160^\circ\text{C}$  which then was maintained for 6 to 30 minutes so that whiskers with different diameters could be obtained. The average magnetic field strength during these runs was 1300 Gauss.

The X-ray analysis of the whiskers was carried out with a G.E. XRD-5 diffractometer for which the whiskers were packed into a standard specimen holder;  $\text{CrK}_\alpha$  radiation was used. Specimens for transmission electron microscopy (TEM) were obtained by placing a small bundle of whiskers between double grids. Normally, an assortment of whiskers with different diameters was present of which the majority exhibited the thickness for which the run had been designed (for example  $10 \mu\text{m}$ ). However, there was always some groups of whiskers of electron transparent diameter to be found which were suitable for grain size determinations and selected area diffraction. For the field-ion microscope study whiskers were separated as far as possible into single fibers approximately 0.5 cm in length, and spot welded onto 0.007 cm diameter chromel wire loops. The whiskers attached to the wire loops were then suspended in an electrolytic solution consisting of 1 part  $\text{HNO}_3$ , 1 part  $\text{HCl}$ , 4 parts  $\text{H}_2\text{O}$ , and slowly electroetched to a fine point using an a.c. voltage of 1-2 volts. The progress of the electro-polishing process was checked periodically using a metallographic microscope at 400 X.

After having prepared suitable electropolished (etched) iron whisker end forms (attached to the chromel wire loops) the chromel loops were inserted into a cold-finger arrangement in a specially designed field-ion microscope and evacuated to  $10^{-7}$  Torr. Images of the end forms were obtained using hydrogen promoted helium imaging (at a gauge pressure of roughly  $10^{-4}$  Torr). The best images were obtained using pure neon as the imaging gas at a gauge pressure of  $10^{-4}$  Torr. Imaging voltages were observed to range from a few Kilovolts to as high as 25 kV. A channel-plate image intensification system coupled with a Nikon-F camera, and using close-up lenses was used in recording the field-ion images of the iron whiskers. Numerous whiskers were observed prior to field-ion microscopy examination in a Hitachi Perkin-Elmer HHS-2R scanning electron microscope operated at 25 kV accelerating potential. Several whiskers were also observed prior to and following observations in the field-ion microscope in a Hitachi Perkin-Elmer H.U. 200F transmission electron microscope at an accelerating potential of 200 kV, utilizing a goniometer-tilt stage. A 500 kV RCA electron microscope and a Siemens Elmiskop IA were also used for transmission electron microscopy and selected area diffraction.

## 2. Results


In view of the very small grain size found in polycrystalline iron whiskers, transmission electron microscopy (TEM) appears to be one of the most suitable techniques for their microstructural investigation. However, since most production runs yield whiskers thicker than  $0.1\text{ }\mu\text{m}$  they are non-transparent to electrons even in high voltage electron




microscopes. This is due to multiple diffraction resulting from a number of grains which compose the whisker diameter in the direction of the incident electron beam (Fig. 1a, 1b). Thinning the whiskers for TEM by etching, electrolytical polishing or ion sputtering generally leads to uneven thicknesses which by itself poses problems in contrast interpretation. Figure 1a shows at the bottom a whisker which is nearly  $0.2\text{ }\mu\text{m}$  thick. However, thinner whiskers are also visible exhibiting partial transparency and a wealth of contrast detail. The evaluation of TEM data, supported by selected area diffraction, leads to the conclusion that both, mass-thickness and diffraction contrast mechanisms, have been responsible for the details exhibited in the micrographs. The possibility of additional detail due to phase-contrast mechanisms is under study. In any event, it can be concluded without ambiguity that the individual grains are not undisturbed but contain regions below  $50\text{ }\text{\AA}$  in size which give rise to distinct contrast phenomena the details of which were not discernable by TEM.

Figure 2 illustrates the typical appearance of an iron whisker spot welded onto a chromel wire loop and electroetched to a fine-pointed emission tip. Figure 3 illustrates several typical field-ion images. These field-ion micrographs are lacking in the surface atomic symmetry and detail normally associated with field-ion images of metal and alloy emission end forms, but they are typical of the images which could be obtained using helium image-gas imaging at  $78^{\circ}\text{K}$ . The images of Figure 3 show several features of the whisker microstructure. First, it should be apparent that there is no "long-range" crystallinity.



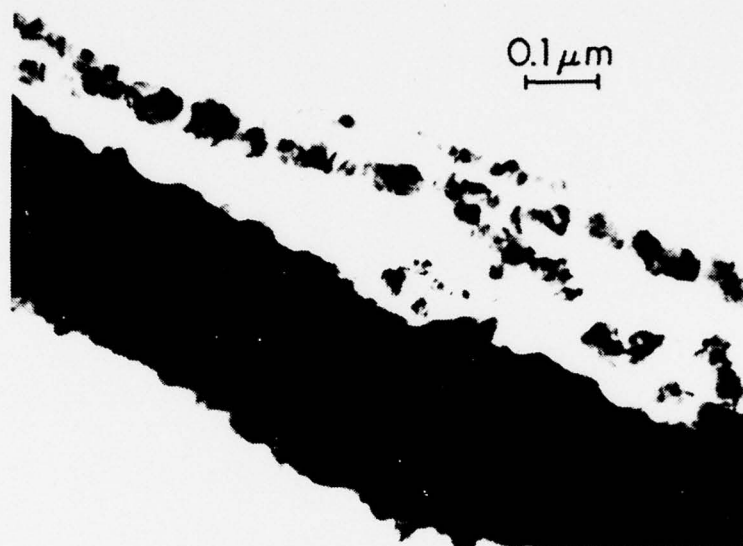

a) 125,000 X

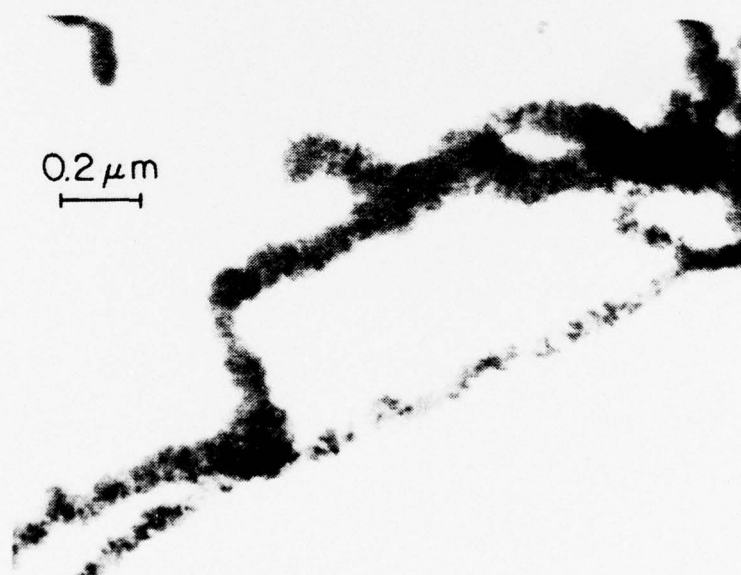

b) 70,000 X

Figure 1 Transmission electron micrographs of polycrystalline iron whiskers, showing grain sizes from a few hundred angstroms to about 50 Å. Inclusions below 50 Å (not resolved) are responsible for the mottled background.



$3\mu\text{m}$   
└───┘

3,500 X


Figure 2 Scanning electron micrograph illustrating an electroetched polycrystalline iron whisker.

Figure 3(a) and (d) show that grain sizes characteristic of individual crystallites are generally about 20 Å. Furthermore, the images in Figure 3 (particularly prominent in Figure 3(a) and (b)) contain numerous, large image points which can be interpreted as being carbon or carbon-like<sup>(4)</sup>, or molecular in nature, i.e. they could be carbides or oxides. Previous X-ray studies have indicated that carbon, carbides, and oxides are incorporated into the whisker microstructure<sup>(5)</sup>. Figure 3 shows that such inclusions are distributed somewhat randomly within the microstructure, and not restricted to the grain boundaries. Figure 3(c) shows the "secondary" structure of the whiskers to be concentric cylindrical shells as previously depicted by Lashmore et.al.<sup>(1)</sup>; the shells are composed of particles 1,000-2,000 Å in diameter, each particle made up of 50-100 Å iron grains. However, Figure 3(c) is from an area near the very core of the whisker and the ring displacements are only on the order of a few atomic diameter.

The fact that the field-ion images are somewhat restricted to short-range order or small crystallite areas is due in part to the fact that the minimum tip radius will be determined to a large extent by the sizes of the crystallites composing the core or center of the individual fibers. In Figure 3(c), the image is formed not only from the central core but also from a few of the concentric cylindrical shells which compose the whisker. In Figures 3(a) and (b), however, only the central core structure forms the image. This is because the electroetching produces a systematic removal of the outer surface shells as the end form or tip is created at the core. Consequently,




- a) Edge-plane structure characteristic of small crystallite of  $\alpha$ -Fe is shown circled. Crystal (grain) sizes measured from these observations averaged roughly 20 Å.

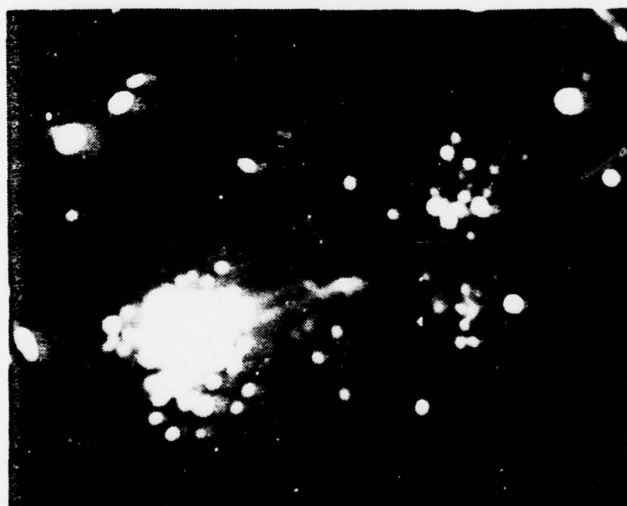


- b) Large image spots and streaks suggestive of inclusions of carbon, carbides or oxides within the microstructure. The structure is characteristically "amorphous".

Figure 3 Field ion images (Neon images) typical of the polycrystalline iron whiskers.

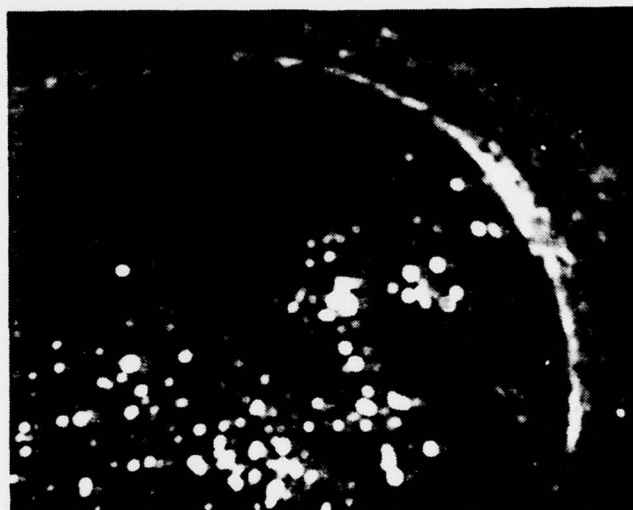

- c) Image showing concentric cylindrical shell structure of whiskers as described by Lashmore et al.<sup>1</sup> but on a much finer scale. These occur close to the core of the whisker and the rings are spaced only one or more atom diameters.

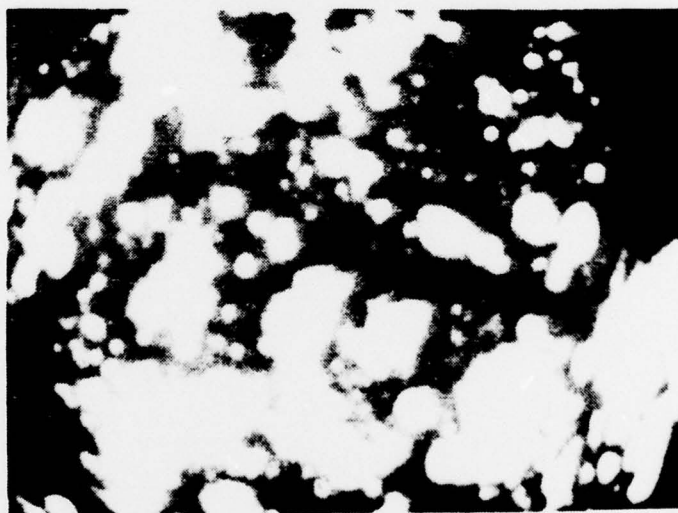

- d) More developed image showing bright "islands" of  $\alpha$ -Fe atoms in a continuous matrix of other atoms of varying identity and range of order which are, for the most part, not visible in the print shown here. The bright "islands" are not always crystalline and many areas of crystallinity are not much different from (a) insofar as size is concerned.



the images of Figures 3(a) and (b) confirm that some of the grains at the actual core are roughly 20 Å. The grain size of  $\alpha$ -iron in the core and in the concentric cylindrical shells surrounding the core, varies between 20 Å and a few hundred angstroms depending on the local conditions governing the CVD process. Figures 3(a), (b) and (d) are illustrating this difference in the grain sizes. Figure 3(d) especially shows that the  $\alpha$ -Fe grains are like islands dispersed in a continuum of other iron atoms and other species which may be oxides and carbides. While Figure 3(d) appears to be representative of a surface containing isolated islands of iron with voids between them, the apparent voids are not voids but simply areas of low image intensity which could not be recorded because of severe contrast restrictions. Nonetheless, with the channel plate of the field-ion microscope at nearly full intensity, the field of Figure 3(d) appeared continuous with atoms. No grain boundaries were apparent, and there was, as noted above, little crystal order in excess of regions measuring 20-50 Å in size. A great deal of the image points were unstable and images of single points (atoms or molecules) would appear, split into two arcs, grow, and disappear as if some gas or other species was being drawn from the specimen by the high field condition. Certainly the image of Figure 3(d) is not a very symmetrical array of atoms typical of an  $\alpha$ -Fe single crystal or even polycrystalline whisker which can be obtained by field-ion microscopy, but it is representative of the structures of the whiskers examined herein. Furthermore, as can be observed from Figure 2, the whiskers prepared

for field-ion microscopy were rather symmetrically electroetched so that the end form actually imaged (Figure 3(d)) represented a region within or very near the core of the whisker.

It is known that the iron whiskers produced by the Schladitz process contain carbon and oxygen<sup>(2,5)</sup>. The carbon content has been confirmed for the whiskers made at the University of Virginia<sup>(6)</sup>, which contain between 1.4 and 1.8 w/o carbon. The oxygen content has been reported by Dawihl and Eicke to be 0.8 w/o<sup>(5)</sup>. X-ray and electron diffraction patterns were obtained in order to determine in which form carbon and oxygen were present in the whiskers. Table 1 lists measurements of d-values from x-ray and electron diffraction patterns together with estimated intensities. Also, the d-values for  $\alpha$ -Fe,  $\alpha$ -Fe<sub>2</sub>O<sub>3</sub>, Fe<sub>3</sub>O<sub>4</sub>, Fe<sub>3</sub>C, and graphite have been listed<sup>(7)</sup> and it is seen that a number of these substances frequently have d-spacings which coincide. X-ray and electron diffraction lines 9, 18, 20, 21 are unambiguously due to  $\alpha$ -Fe. The presence of Fe<sub>3</sub>O<sub>4</sub> and Fe<sub>3</sub>C is clearly indicated in the x-ray diffraction data and, taking into account the overlap, the agreement with expected intensities is fair. Traces of  $\alpha$ -Fe<sub>2</sub>O<sub>3</sub> seem to be present, but graphite is not indicated.

Electron diffraction patterns hold some special interest for the analysis in that four lines are made up primarily from spots while the remaining five lines have a uniform intensity. All spotty lines are associated with  $\alpha$ -Fe rings while lines 1, 2, 4, 15 and 17 have the d-spacings of Fe<sub>3</sub>O<sub>4</sub>. Although lines 4 and 15 coincide with d-spacings of Fe<sub>3</sub>C, the intensities of the former are (100) and (85)

compared to the intensities of  $\text{Fe}_3\text{C}$  (5) and (7). Also, the strongest  $\text{Fe}_3\text{C}$  line, No. 3, is absent in the electron diffraction pattern. The spottiness of the iron rings was to be expected from the electron micrographs and agrees well with the grain size measurements of up to 300 Å. The rings ascribed to  $\text{Fe}_3\text{O}_4$  with their homogeneous intensity, on the other hand, must be caused by crystals less than 50 Å in size.

### 3. Discussion and Summary

The picture which emerges for the whisker microstructure in the present investigation provides an insight which is essential for explaining the extraordinary high strength of the polycrystalline filaments. It has become clear that the microstructure is not a continuous polycrystalline regime but more appropriately characterized as a complex dispersion of fine  $\alpha$ -Fe grains ranging in size from 20-200 Å within an assemblage of minute iron, iron oxide, iron carbide, and possibly carbon particles which in a sense bind the microstructure together. These regions, in relation to the larger crystallites of  $\alpha$ -Fe, are approximately the same size judging from the field-ion micrographs (see Figure 3). This nearly amorphous regime is not an amorphous grain boundary region separating  $\alpha$ -Fe, but rather a multi-phase region. Grain boundaries separating  $\alpha$ -Fe in the sense of a well-defined interface are probably not very prominent as can be envisioned in Figure 3(d). The microstructure as emerging from this investigation also explains the lack of porosity or microporosity in the filaments.

It is the unique and complex microdispersion coupled with the very small  $\alpha$ -Fe crystallite sizes which not only accounts for the very high strength of these whiskers but also the ability to handle them and work with them in a manner not possible with single-crystal whiskers. The incorporation of oxides, carbides, and atomic carbon into this regime might cause a mixing of strong covalent binding with the metallic binding in the iron polycrystals, and this could contribute substantially to the high strength and integrity of the total whisker microstructure.



#### REFERENCES

1. D.S. Lashmore, W. A. Jesser, D. M. Schladitz, H. J. Schladitz and H. G. F. Wilsdorf, J. Appl. Phys. 48, (1977), 478.
2. H. J. Schladitz, Z. Metallkd., 59 (1968) 18.
3. H. J. Schladitz, German Patent No. 1224934 (1964), U. S. Patent No. 3441408 and No. 3570829 (1969/1971).
4. L. E. Murr and O. T. Inal, J. Appl. Phys., 42, (1971) 3887.
5. W. Dawihl and W. Eicke, Powder Met. Int., 3, (1971) 75.
6. D. S. Lashmore, Ph.D. Thesis, University of Virginia, (1977).
7. X-Ray Powder Data File, ASTM, (1960).



Table 1. X-Ray and Electron Diffraction Data from Whiskers

Ref. No.	X-ray Diff.	d-values					Electron Diffraction
		$\alpha$ -Fe	$\text{Fe}_3\text{O}_4$	$\text{Fe}_3\text{C}$	$\alpha$ - $\text{Fe}_2\text{O}_3$	Graphite	
1	2	3	4	5	6	7	8
1			4.85 (40)		3.66 (25)	3.36 (100)	4.81 w cont.
2	2.98 (4)		2.97 (70)				2.99 w cont.
3	2.68 (6)				2.69 (100)		
4	2.54 (21)		2.53 (100)	2.54 (5)			2.56 m cont.
					2.51 (50)		
			2.42 (10)				
5	2.40 (12)		2.38 (65)	2.38 (65)			
6	2.28 (10)			2.26 (25)			
7	2.23 (10)			2.20 (25)			
						2.13 (10)	
8	2.10 (14)		2.09 (70)	2.10 (60)			
				2.06 (70)			
9	2.03 (st)	2.03 (100)		2.02 (60)	2.02 (30)	2.03 (50)	2.03 st spotty
				2.01 (100)			
10	1.94 (9)			1.97 (55)			
11	1.88 (12)			1.87 (30)			
12	1.86 (16)			1.85 (40)		1.80 (5)	
13	1.76 (6)			1.75 (15)			
14	1.69 (5)		1.71 (60)	1.69 (15)	1.70 (60)	1.68 (30)	
15	1.62 (7)		1.61 (35)	1.61 (7)			1.62 w cont.
16	1.59 (8)			1.58 (20)		1.54 (10)	
17	1.49 (10)		1.48 (85)		1.48 (35)		1.49 m cont.
					1.45 (35)		
18	1.43 (100)	1.43 (19)					1.43 m spotty
19	1.32 (5)		1.32 (20)				
						1.23 (30)	
20	1.17 (st)	1.17 (30)				1.16 (50)	1.16 st spotty
						1.14 (5)	
						1.12 (20)	
21	1.01 (32)	1.013 (9)					1.04 w spotty

( ) estimated intensities

w = weak int.

m = medium int.

st = strong int.

cont. = continuous rings

spotty = spots in rings

# DISTRIBUTION LIST

## Copy No.

1 - 106	Basic Distribution List and Supplementary Distribution List
107 - 118	H. G. F. Wilsdorf
119	I. A. Fischer
120 - 121	E. H. Pancake Science/Technology Information Center Clark Hall
122	K.R. Lawless
123	RLES Files

# BASIC DISTRIBUTION LIST

Technical and Summary Reports

April 1978

<u>Organization</u>	<u>Copies</u>	<u>Organization</u>	<u>Copies</u>
Defense Documentation Center Cameron Station Alexandria, VA 22314	12	Naval Air Propulsion Test Center Trenton, NJ 08628 ATTN: Library	1
Office of Naval Research Department of the Navy 800 N. Quincy Street Arlington, VA 22217		Naval Construction Battalion Civil Engineering Laboratory Port Hueneme, CA 93043 ATTN: Materials Division	1
ATTN: Code 471	1	Naval Electronics Laboratory San Diego, CA 92152 ATTN: Electron Materials Sciences Division	1
Code 102	1		
Code 470	1		
Commanding Officer Office of Naval Research Branch Office Building 114, Section D 666 Summer Street Boston, MA 02210	1	Naval Missile Center Materials Consultant Code 3312-1 Point Mugu, CA 92041	1
Commanding Officer Office of Naval Research Branch Office 536 South Clark Street Chicago, IL 60605	1	Commanding Officer Naval Surface Weapons Center White Oak Laboratory Silver Spring, MD 20910 ATTN: Library	1
Office of Naval Research San Francisco Area Office 760 Market Street, Room 447 San Francisco, CA 94102	1	David W. Taylor Naval Ship Research and Development Center Materials Department Annapolis, MD 21402	1
Naval Research Laboratory Washington, DC 20375		Naval Undersea Center San Diego, CA 92132 ATTN: Library	1
ATTN: Codes 6000	1	Naval Underwater System Center Newport, RI 02840 ATTN: Library	1
6100	1		
6300	1		
6400	1		
2627	1	Naval Weapons Center China Lake, CA 93555 ATTN: Library	1
Naval Air Development Center Code 302 Warminster, PA 18964 ATTN: Mr. F. S. Williams	1	Naval Postgraduate School Monterey, CA 93940 ATTN: Mechanical Engineering Department	1

BASIC DISTRIBUTION LIST (cont'd)

<u>Organization</u>	<u>Copies</u>	<u>Organization</u>	<u>Copies</u>
Naval Air Systems Command Washington, DC 20360 ATTN: Codes 52031 52032	1	NASA Headquarters Washington, DC 20546 ATTN: Code:RRM	1
Naval Sea System Command Washington, DC 20362 ATTN: Code 035	1	NASA Lewis Research Center 21000 Brookpark Road Cleveland, OH 44135 ATTN: Library	1
Naval Facilities Engineering Command Alexandria, VA 22331 ATTN: Code 03	1	National Bureau of Standards Washington, DC 20234 ATTN: Metallurgy Division Inorganic Materials Div.	1 1
Scientific Advisor Commandant of the Marine Corps Washington, DC 20380 ATTN: Code AX	1	Director Applied Physics Laboratory University of Washington 1013 Northeast Forthieth Street Seattle, WA 98105	1
Naval Ship Engineering Center Department of the Navy Washington, DC 20360 ATTN: Code 6101	1	Defense Metals and Ceramics Information Center Battelle Memorial Institute 505 King Avenue Columbus, OH 43201	1
Army Research Office P.O. Box 12211 Triangle Park, NC 27709 ATTN: Metallurgy & Ceramics Program	1	Metals and Ceramics Division Oak Ridge National Laboratory P.O. Box X Oak Ridge, TN 37380	1
Army Materials and Mechanics Research Center Watertown, MA 02172 ATTN: Research Programs Office	1	Los Alamos Scientific Laboratory P.O. Box 1663 Los Alamos, NM 87544 ATTN: Report Librarian	1
Air Force Office of Scientific Research Bldg. 410 Bolling Air Force Base Washington, DC 20332 ATTN: Chemical Science Directorate Electronics & Solid State Sciences Directorate	1 1	Argonne National Laboratory Metallurgy Division P.O. Box 229 Lemont, IL 60439	1
Air Force Materials Laboratory Wright-Patterson AFB Dayton, OH 45433	1	Brookhaven National Laboratory Technical Information Division Upton, Long Island New York 11973 ATTN: Research Library	1
Library Building 50, Rm 134 Lawrence Radiation Laboratory Berkeley, CA	1	Office of Naval Research Branch Office 1030 East Green Street Pasadena, CA 91106	1



M  
January 1978

SUPPLEMENTARY DISTRIBUTION LIST

Technical and Summary Reports

Professor G. S. Ansell  
Rensselaer Polytechnic Institute  
Dept. of Metallurgical Engineering  
Troy, New York 12181

Professor H. K. Birnbaum  
University of Illinois  
Department of Metallurgy  
Urbana, Illinois 61801

Dr. E. M. Breinan  
United Aircraft Corporation  
United Aircraft Res. Laboratories  
East Hartford, Connecticut 06108

Professor H. D. Brody  
University of Pittsburgh  
School of Engineering  
Pittsburgh, Pennsylvania 14213

Mr. P. J. Cacciatore  
General Dynamics  
Electric Boat Division  
Eastern Point Road  
Groton, Connecticut 06340

Professor J. B. Cohen  
Northwestern University  
Dept. of Material Sciences  
Evanston, Illinois 60201

Professor M. Cohen  
Massachusetts Institute of Technology  
Department of Metallurgy  
Cambridge, Massachusetts 02139

Professor Thomas W. Eagar  
Massachusetts Institute of Technology  
Department of Materials  
Science and Engineering  
Cambridge, Massachusetts 02139

Professor B. C. Giessen  
Northeastern University  
Department of Chemistry  
Boston, Massachusetts 02115

Dr. G. T. Hahn  
Battelle Memorial Institute  
Department of Metallurgy  
505 King Avenue  
Columbus, Ohio 43201

Professor D. G. Howden  
Ohio State University  
Dept. of Welding Engineering  
190 West 19th Avenue  
Columbus, Ohio 43210

Dr. C. S. Kortovich  
TRW, Inc.  
23555 Euclid Avenue  
Cleveland, Ohio 44117

Professor D. A. Koss  
Michigan Technological University  
College of Engineering  
Houghton, Michigan 49931

Professor A. Lawley  
Drexel University  
Dept. of Metallurgical Engineering  
Philadelphia, Pennsylvania 19104

Professor Harris Marcus  
The University of Texas at Austin  
College of Engineering  
Austin, Texas 78712

Dr. H. Margolin  
Polytechnic Institute of New York  
333 Jay Street  
Brooklyn, New York 11201

Professor K. Masubuchi  
Massachusetts Institute of Technology  
Department of Ocean Engineering  
Cambridge, Massachusetts 02139

Dr. H. I. McHenry  
National Bureau of Standards  
Institute for Basic Standards  
Boulder, Colorado 80302

## SUPPLEMENTARY DISTRIBUTION LIST (Cont'd)

Professor J. W. Morris, Jr.  
University of California  
College of Engineering  
Berkeley, California 94720

Professor Ono  
University of California  
Materials Department  
Los Angeles, California 90024

Dr. Neil E. Paton  
Rockwell International  
Science Center  
1049 Camino Dos Rios  
P.O. Box 1085  
Thousand Oaks, California 91360

Mr. A. Pollack  
Naval Ships Research & Development  
Center  
Annapolis, Maryland 21402

Dr. Karl M. Prewé  
United Technologies Laboratories  
United Technologies Corporation  
East Hartford, Connecticut 06108

Professor W. F. Savage  
Rensselaer Polytechnic Institute  
School of Engineering  
Troy, New York 12181

Professor O. D. Sherby  
Stanford University  
Materials Sciences Division  
Stanford, California 94300

Professor J. Shyne  
Stanford University  
Materials Sciences Division  
Stanford, California 94300

Dr. R. P. Simpson  
Westinghouse Electric Corporation  
Research & Development Center  
Pittsburgh, Pennsylvania 15235

Dr. E. A. Starke, Jr.  
Georgia Institute of Technology  
School of Chemical Engineering  
Atlanta, Georgia 30332

Professor David Turnbull  
Harvard University  
Division of Engineering and  
Applied Physics  
Cambridge, Massachusetts 02139

Dr. F. E. Wawner  
University of Virginia  
School of Engineering and Applied  
Science  
Charlottesville, Virginia 22901

Dr. C. R. Whitsett  
McDonnell Douglas Research  
McDonnell Douglas Corporation  
Saint Louis, Missouri 63166

Dr. J. C. Williams  
Carnegie-Mellon University  
Department of Metallurgy and  
Materials Sciences  
Schenley Park  
Pittsburgh, Pennsylvania 15213

Professor H. G. F. Wilsdorf  
University of Virginia  
Charlottesville, Virginia 22903

Dr. M. A. Wright  
University of Tennessee  
Space Institute  
Tullahoma, Tennessee 37388